

## PROPERTIES OF AUSTEMPERED DUCTILE IRON

Sudhanshu Detwal<sup>1\*</sup>, Deivanathan R<sup>2</sup>

<sup>1</sup>*M. Tech. (CAD/CAM), SMBS, VIT University- Chennai Campus, Chennai  
600127, India*

<sup>2</sup>*Associate Professor, SMBS, VIT University- Chennai Campus, Chennai  
600127, India*

*Received 28.12.2015*

*Accepted 04.03.2016*

### Abstract

This work concerns microstructural and mechanical properties of an austempered ductile cast iron (ADI). The ductile iron material was produced by the sand mould casting technique. Afterwards, austempering heat treatment was applied to the specimens at two different temperatures of 250°C and 350°C. Austempered Ductile Irons (ADIs) were produced successfully by different two-stage heat treatments, to obtain favorable microstructure and hardness. The microstructure and hardness obtained by such variable heat treatments were compared. The austempering temperature and time were found to be decisive parameters in obtaining a desired ADI microstructure.

*Key words: austempering, ADI, microstructure*

### Introduction

Austempered ductile iron (ADI) is considered as a new kind of engineering material and shows good combinations of high strength, ductility, toughness, fatigue strength and wear resistance. Considerable research have been conducted on microstructure and mechanical performance of austempered ductile iron[1,2]. The attractive properties of ADI are due to its unique microstructure which consists of high carbon austenite and bainitic ferrite with graphite nodules dispersed in the matrix. Nowadays, it has been used to manufacture many equipments, tools and components such as gears and crankshafts. ADI was first developed for heavy load gear wheels in Finland in 1973[3]. With the development of ADI, standards for ADI have also been published. In ASTM standard 897 M-06, there are 6 grades of ADI according to the ultimate tensile strength [4, 12]. However, researches on ADIs are related primarily to the austempering process parameters, viz., austempering time and temperature, rather than to the standard ADI strength grade, which can be confusing to the designer of ADI

---

\* Corresponding author: Sudhanshu Detwal, [deivanathan.r@vit.ac.in](mailto:deivanathan.r@vit.ac.in)

structures [5-7]. Thus, microstructure and properties of ADI with different strength grades should be studied in detail to supply useful information for the ADI makers and component designers.

In this study, four ADIs samples were prepared; the microstructure was analysed, and hardness tests were conducted and correlated with austempering parameters.

## Experimental work

### Materials

The composition of the ductile iron (S G iron) used in this study is shown in Table 1. The ductile iron was cast in solid cylindrical shape by sand casting technique. The dimensions of the ductile iron specimen used in our experiments are as shown in Fig.1.

Table 1. Composition of examined SG iron specimen

| Element | C    | Si   | Mn   | P    | S    | Cr   | Mo    | Ni    | Fe |
|---------|------|------|------|------|------|------|-------|-------|----|
| Wt.%    | 3.86 | 3.04 | 0.73 | 0.03 | 0.05 | 0.02 | <0.02 | <0.06 |    |

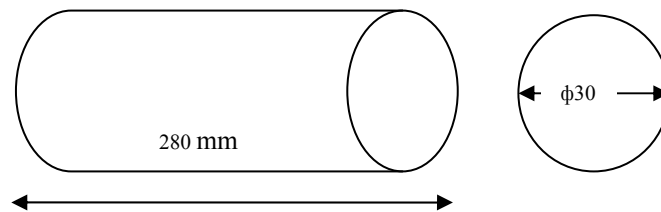


Fig. 1. Dimensions of ADI specimen

### Methodology

The production of ADI in general, is constituted by a two stage heat treatment cycle. In the first stage of heat treatment, the specimen is heated in a furnace up to a little above the austenitizing temperature (i.e) 980°C and soaked at that point for 120min., to ensure that the entire cross section of the specimen has uniform microstructure. Austenitization is followed by the second stage, (i.e) austempering, which consists of rapidly transferring the specimen from the furnace into a salt bath wherein isothermal transformation of austenite occurs over a period of time specified by the soaking time. Subsequently the specimen is allowed to cool down to room temperature, and this rate of cooling is not a significant issue for cast irons.

The two stage heat treatment cycle followed in producing ADI has been summarized in Table 2. In this study, the austenitizing condition is the same for all specimens. But, the isothermal transformation is allowed to occur at two specific temperatures viz., 250°C and 350°C, extending either upto 60 min. or upto 120min. After the heat treatments, samples for microstructure observation, hardness test, were taken from the bottom of those blocks.

The samples were etched in 4% nital solution at room temperature after being polished, and then they were observed by an optical microscope. The graphite morphology was rated for the nodularity and nodule count in accordance with the ASTM standard A247.

Brinell hardness tests were carried out in the Brinell hardness testing machine with a load of 187.5kg and 2.5mm WC ball indenter. For each specimen, 5 readings were taken and averaged to represent the hardness values in BHN.


Table 2. Heat treatment plan for the production of four ADI specimen

|            | Stage 1: Austenitization |                   | Stage 2: Austempering |                   |
|------------|--------------------------|-------------------|-----------------------|-------------------|
|            | Temperature, °C          | Soaking time, min | Temperature, °C       | Soaking time, min |
| Specimen 1 | 930                      | 120               | 250                   | 60                |
| Specimen 2 | 930                      | 120               | 250                   | 120               |
| Specimen 3 | 930                      | 120               | 350                   | 60                |
| Specimen 4 | 930                      | 120               | 350                   | 120               |


## Results and discussions

### Microstructure

The microstructures of the samples observed by optical microscope are shown in Fig. 2. All the austempered microstructures show a matrix consisting of a two-phase mixture of a dark etching bainitic ferrite, which is needle shaped, and the bright etching stabilized austenite with graphite nodules dispersed in it. The length of the ferrite needles was found to decrease with the increasing of austempered temperature and time. Austempering at 350°C is likely to produce a mixed ADI structure, due to early formation of pearlite caused by reacted austenite [8]. The microstructure of sample 1, in Fig. 2, shows well preserved tempered nodular graphite in the matrix mostly consisting of bainite and ferrite structure, having nodularity – 40% and nodule count – 30%. The microstructure of sample 2 is characterized by well-preserved tempered nodular graphite in the matrix mostly consisting of bainite and ferrite structure, having nodularity – 30% and nodule count – 25%. The microstructure of sample 3 is shows well preserved tempered nodular graphite in a matrix mostly consisting of bainite and ferrite, having nodularity – 40% and nodule count – 50%. The nodularity is rather low, known to be influenced by the charge quality and melting technique [9].

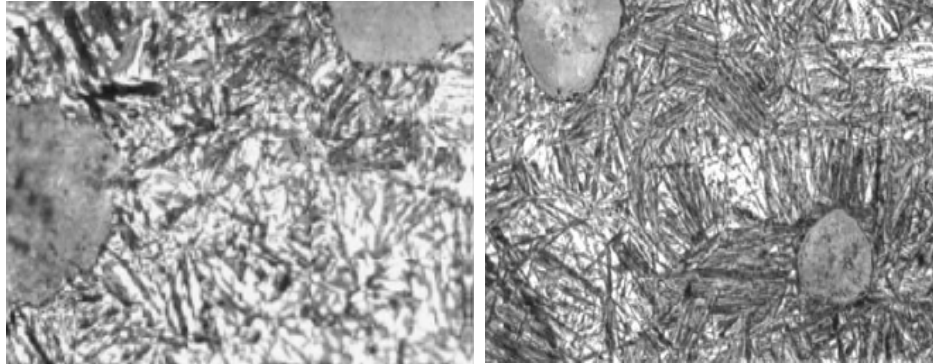

*Sample 1(100X) processed at 250°C, 1hr    Sample 2(100X) processed at 250°C, 2hr*

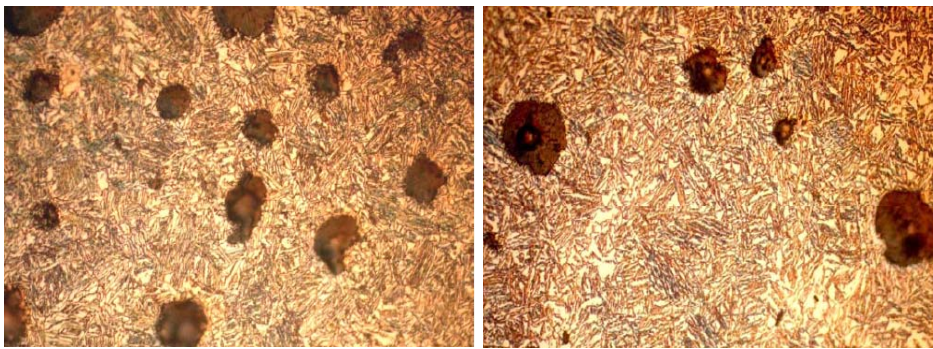

*Sample 3(100X) processed at 350°C, 1hr    Sample 4(100X) processed at 350°C, 2hr*

*Fig.2 The effect of heat treatment parameters on the microstructure of ADI*

#### *Hardness*

The hardness of ADI specimen is shown in Table 3, with the corresponding austempering parameters. It can be seen that with the increase of austempered temperature the hardness of ADI decreases, however for increasing austempered time hardness increase at 250°C but decreases at 350°C. Therefore, as the stabilized austenite content increases the hardness decreases. High austempering temperature prevents the formation of martensite, a hard phase, usually formed in case of low austempering temperature [10]. When the austempering temperature decreases from 350°C to 250°C, the morphology of bainitic ferrite changes from upper to lower. Therefore, the austempering temperature and time are found to be decisive parameters and hence need to be optimized.

The hardness value specified by ASTM 897M -06 for ADI Grade 750/500/11 is 241BHN at the minimum and is greater for higher grades [12]. The ADI specimens produced in this study, have their hardness in the range of 198-213BHN. The lower value could be related to the initial composition of the ductile iron raw material. Further,

it is to be noted that a section size greater than 19mm would require alloying additions (of Cu, Ni, Mo) to improve the hardenability [13].

Table 3. Effect of austempering conditions on the hardness of ADI

| Specimen No. | Austempering condition | Hardness |
|--------------|------------------------|----------|
| 1.           | 250°C 1hr              | 209 BHN  |
| 2.           | 250°C 2hr              | 212 BHN  |
| 3.           | 350°C 1hr              | 213 BHN  |
| 4.           | 350°C 2hr              | 198 BHN  |

### Conclusion

Considering the results of this study, the following conclusions can be made:

1. The austempering temperature and time have significant influence on microstructures of ADIs. When the austempering temperature decreases from 350°C to 250°C, the morphology of bainitic ferrite changes from upper to lower.
2. As the austempered temperature decreases from 350°C to 250°C, the hardness increases.
3. As the time increases for 350°C, from 1 hour to 2 hour hardness decrease and for 250°C, from 1 hour to 2 hour hardness increases.
4. High austempering temperature prevents the formation of martensite usually formed in low austempering temperature.

### References

- [1] K.B. Rundman, In: Proceedings of World Conference on Austempered Ductile Iron, Bloomington, IL, 1991, p1.
- [2] R. Gundlach, J. Jaowak, In: Proceedings of 2nd International Conference on Austempered Ductile Iron: Your means to improved performance, productivity and cost, University of Michigan, Ann Arbor, MI, 1986, p23.
- [3] Avdusinovic Hasan, Almaida Gigoric, In: Proceedings of 18<sup>th</sup> International research conference on Trends in the development of machining and associated technologies, Budapest, Hungary, 2014, p53.
- [4] GB/T 24733, Austempered ductile iron (ADI) castings, Chinese Standards (GB), 2009.
- [5] G. Balachandran, A. Vadiraj, M. Kamaraj, E. Kazuya, Mater. Des. 32 (2011) 4042–4049.
- [6] S.K. Putatunda, Mater. Sci. Eng., A. 315 (2001) 70-80.
- [7] O. Eric, L. Sidjanin, Z. Miskovic, S. Zec, MT. Jovanovic, Mater. Lett. 58 (2004) 2707-2711.
- [8] BV. Kovacs, Modern Casting, 36 (1990) 38–41.
- [9] Parejiya Pavan. P, Effect of austempering behavior of ductile iron, M.Tech Thesis, Ganpat University, India, 2014.
- [10] M. Kaczorowski, A. Krzynska, Arch. Foundry Eng. 7(1) (2007) 161-166.
- [11] W.F. Smith, Structure and Properties of Engineering Alloys, third ed., McGraw-Hill, New York, 1993.
- [12] Standard Specification for Austempered Ductile Iron Castings, ASTM International, 2006.
- [13] K.L.Hayrynen, In: Proceedings of World Conference on ADI, Kentucky, USA, 2002.